

Quantitative Determination of Performance Loss due to Cell Cracks using EL Images (PV-5)



A joint India-U.S. research consortium funded under the Joint Clean Energy Research & Development Center (JCERDC)

Scientific Achievement:

We correlated inactive areas in an electroluminescence (EL) image to the short-circuit current loss of the solar cells.


Significance and Impact:

Electroluminescence images can be used to estimate the degradation in the module current. *In-situ* EL imaging can emerge as an alternative to module I-V measurements for fielded PV systems.


Research Details:

- EL image of a PV module is converted into binary image using thresholding function, considering the mode of the image histogram as the threshold limit.
- Calculated the active cell area from the binary EL image.
- For quantum efficiency (QE) and I-V measurements, three cells were selected (worst, medium, and best in EL image) and their cell interconnects accessed by cutting through the backsheet.
- Each cell is divided into three sections demarcated by the two busbars, and the QE is measured at 30 different points in these three sections (in the three selected cells).
- The average QE is calculated for each cell, and based on it, the short-circuit current is calculated.
- For each cell, the short-circuit current is also measured on a solar simulator.

Publication: Carlos Castaneda *et al.*, Field Inspection of PV Modules: Quantitative Determination of Performance Loss due to Cell Cracks using EL Images, NREL PV Module Reliability Workshop, Denver, CO (2017).

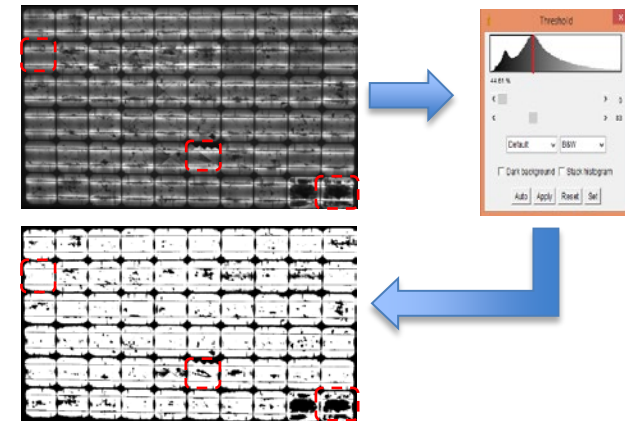

Conversion of EL image into binary image using thresholding technique

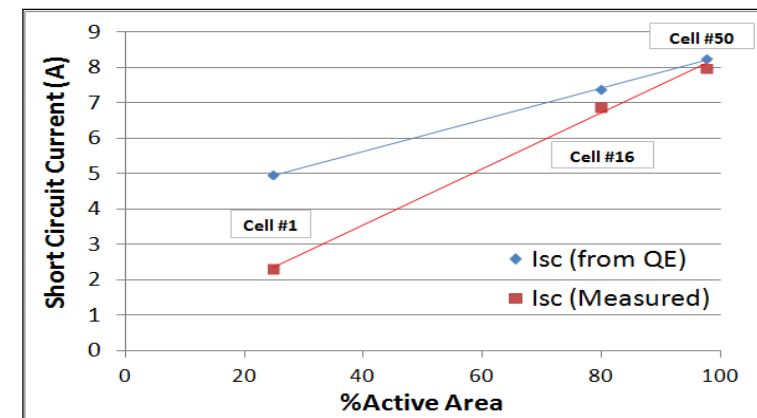

Short-circuit current (I_{sc}) based on integrated QE and direct measurements, plotted against the percentage active area of cell

Contact: G. Tamizhmani (manit@asu.edu)



U.S. DEPARTMENT OF ENERGY



NREL NATIONAL RENEWABLE ENERGY LABORATORY



Sandia National Laboratories

STEP

RAND CORPORATION